

M. KWAPISZ*, M. KNAPIŃSKI*, H. DYJA*, K. LABER*

ANALYSIS OF THE EFFECT OF THE TOOL SHAPE ON THE STRESS AND STRAIN DISTRIBUTION IN THE ALTERNATE EXTRUSION AND MULTIAXIAL COMPRESSION PROCESS

ANALIZA WPŁYWU KSZTAŁTU NARZĘDZI NA ROZKŁAD NAPRĘŻEŃ I ODKSZTAŁCENI W PROCESIE NAPRZEMIENNEGO WYCISKANIA I ŚCISKANIA WIELOOSIOWEGO

The paper presents the results of numerical simulations of the alternate indirect extrusion and multiaxial compression process, performed using commercial software designed for the thermomechanical analysis of plastic working processes, Forge 2009. The novel method of alternate indirect extrusion and multiaxial compression, proposed by the authors, is characterized by the occurrence of strain states in the material being plastically worked, which are similar to those occurring in the equal channel angular pressing and cyclic extrusion compression processes.

It can be found from preliminary studies carried out that the two alternate operations, i.e. extrusion and multiaxial compression, result in a strain accumulation and the formation of a strain state particularly favourable to grain refinement.

As shown by preliminary numerical studies performed by the authors, a zone of large plastic strains forms at the lateral side of the stamping during extrusion of material, which gradually fades along the stamping axis direction. After the multiaxial compression operation, when the material has been brought again to its original shape, the large strains zone moves and then settles in the form of a torus under the stamp. The subsequent extrusion process results in the formation of a new large strains zone being located at the lateral stamping side, and, at the same time, the displacement of the previously deformed material towards its axis. Repeating the above operations many times should bring about large magnitudes of homogeneous deformation within the entire volume of the material examined. The main problem during carrying out practical tests will be to determine the optimal shapes of dies and stamps, which would assure the intended strain state to be obtained in the material, and would also prevent the buckling and overlaps of the material during multiaxial compression.

The distribution of stresses and strains occurring during the compression tests and their correlation with the MaxStrain tests were analyzed within the work. The performed numerical simulations will enable the determination of the proper parameters of the compression test on the Gleeble simulator in order to obtain the strain accumulation which will allow a considerable refinement of the structure.

Keywords: alternate extrusion and multiaxial compression, large plastic strain processes, nano-materials

W pracy przedstawiono wyniki symulacji numerycznych uzyskane za pomocą komercyjnego oprogramowania do termomechanicznej analizy procesów przeróbki plastycznej Forge 2009 procesu naprzemiennego wyciskania przeciwbieżnego i ściskania wieloosiowego. Zaproponowana przez autorów nowa metoda naprzemiennego wyciskania przeciwbieżnego i wieloosiowego ściskania, charakteryzuje się występowaniem w przerabianym plastycznie materiale stanów odkształcenia podobnych do występujących w procesach przepychania przez kanał kątowy i cyklicznego wyciskania ściskającego.

Z wykonanych badań wstępnych można wnioskować, że w wyniku połączenia i powtarzania dwóch naprzemiennych operacji: wyciskania i ściskania wieloosiowego następuje akumulacja odkształcenia i wytworzenie stanu odkształcenia szczególnie sprzyjającego rozdrobnieniu ziarna.

Jak wynika ze wstępnych badań numerycznych, przeprowadzonych przez autorów, podczas wyciskania materiału powstaje strefa dużych odkształceń plastycznych przy powierzchni bocznej wypraski, stopniowo zanikająca w kierunku jej osi. Po operacji wieloosiowego ściskania, gdy materiał zostaje powtórnie doprowadzony do początkowego kształtu, strefa dużych odkształceń ulega przemieszczeniu i lokalizuje się w obszarze w postaci torusa pod stemplem. Kolejny proces wyciskania spowoduje utworzenie nowej strefy dużych odkształceń zlokalizowanej przy powierzchni bocznej wypraski i jednocześnie przemieszczanie uprzednio odkształconego materiału w kierunku jego osi. Wielokrotne powtarzanie opisanych zabiegów powinno w efekcie doprowadzić do uzyskania w całej objętości badanego materiału dużych wartości jednorodnego odkształcenia. Głównym problemem podczas realizacji badań praktycznych będzie określenie optymalnych kształtów matryc i stempli, które

* CZĘSTOCHOWA UNIVERSITY OF TECHNOLOGY, FACULTY OF MATERIAL PROCESSING TECHNOLOGY AND APPLIED PHYSICS, INSTITUTE OF MODELLING AND AUTOMATION OF PLASTIC WORKING PROCESSES, 42-200 CZĘSTOCHOWA, 19 ARMII KRAJOWEJ AV., POLAND

zagwarantują uzyskanie zamierzonego stanu odkształcenia w materiale, a ponadto uniemożliwią wyboczenie i zaprasowania materiału podczas wieloosiowego ściskania.

W pracy analizowano rozkład naprężeń i odkształceń występujących podczas prób ściskania i ich korelacja z próbami MaxStrain. Przeprowadzone symulacje numeryczne umożliwią ustalenie prawidłowych parametrów próby ściskania w symulatorze Gleeble w celu uzyskania akumulacji odkształcenia co umożliwi znaczne rozdrobnienie struktury.

1. Introduction

Materials of an ultrafine-grained and nanometric structure exhibit mechanical properties that often surpass those of conventionally obtained materials having phases or grain structures on a micrometric scale. Moreover, the ultrafine microstructure, in the sub-micrometric or nanometric range, results in new and extraordinary physical properties, such as: a decrease in Young's modulus, a reduction in the Debye and Curie temperatures, an increase in the diffusion degree, an enhancement of corrosion resistance, and an improvement in magnetic properties. Many studies indicate that by using processes that cause a strain accumulation, materials can be obtained, which combine high strength with high plasticity.

Ultrafine-grained microstructures can be obtained in thermoplastic working processes with applying severe plastic deformations (SPD) to ordinary materials. The core of the SPD processes is the capability to obtain a very large deformation of material and the rearrangement of strain-induced dislocations, which results in a very strong grain refinement [1, 4, 5].

Among the SPD processes that take advantage of large plastic strain, the most common include:

- Equal Channel Angular Pressing (ECAP),
- High-Pressure Torsion (HPT),
- Multi-axial Forging (MF),
- Cyclic Extrusion Compression (CEC),
- Repetitive Corrugation and Straightening (RCS), and
- Accumulative Roll-Bonding (ARB).

The severe metal deformation processes have a significant impact on the structure and properties of materials. Ultrafine-grained structures and nanostructures can be characterized as being unique owing to their physical and mechanical properties, such as: high low-temperature strength and/or high stress superplasticity and others [2÷9].

During applying high deformations, a strain anisotropy occurs in the material, which causes the anisotropy of mechanical properties. The alternate extrusion and multiaxial compression method proposed by the authors, as illustrated schematically in Fig. 1, is characterized by the occurrence of strain states in the material being plastically worked, which are similar to those occurring in the equal channel angular pressing and cyclic extrusion compression processes.

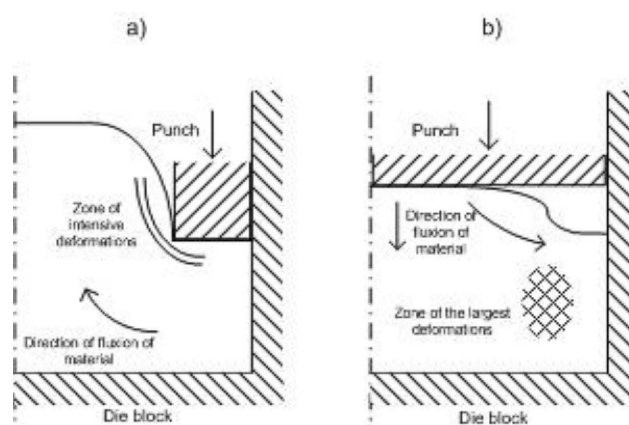


Fig. 1. Schematic of the alternate extrusion and multiaxial compression process; a) extrusion operation; b) compression operation

As shown by the preliminary numerical studies, a zone of large plastic strains forms at the lateral side of the stamping during extrusion of the material, which gradually fades along the stamping axis direction (Fig. 1a). After the multiaxial compression operation, when the material has been brought again to its original shape, the large strains zone moves and then settles in the form of a torus under the stamp (Fig. 1b). The subsequent extrusion process results in the formation of a new large strains zone being located at the lateral stamping side, and, at the same time, the displacement of the previously deformed material towards its axis. Repeating the above operations many times should bring about large magnitudes of homogeneous deformation within the entire volume of the material examined. The main problem will be to determine the optimal shapes of dies and stamps, which will assure the intended strain state to be obtained in the material, and will also prevent the buckling and overlaps of the material during multiaxial compression.

2. Numerical modelling

The Forge 2009® software relies on the finite element method and is designed for modelling of plastic working processes. The software enables modelling of plastic working processes in a spatial strain state. A plastically deformed medium is described by the equation based on the Norton-Hoff law:

$$S_{ij} = 2K_0 (\bar{\epsilon} + \epsilon_0)^{n_0} \cdot e^{(-\beta_0 * T)} \left(\sqrt{3} \dot{\bar{\epsilon}} \right)^{m_0 - 1} \dot{\epsilon}_{ij}, \quad (1)$$

where: S_{ij} – stress tensor deviator; $\dot{\bar{\epsilon}}$ – strain rate intensity; $\dot{\epsilon}_{ij}$ – strain rate tensor; $\bar{\epsilon}$ – strain intensity,

ε_0 – base strain, T – temperature, K_0, m_0, n_0, β_0 – material constants specific to the plastically worked material.

A general form of this law is as follows:

$$\sigma = 2K \left(\sqrt{3} \dot{\varepsilon}_i \right)^{m-1} \dot{\varepsilon} \quad (2)$$

The coefficient m in Eq. (3) may assume the following values: $m = 1$ corresponds to a Newtonian liquid with a viscosity of $\eta = 2K$, $m = 0$ gives a plastic flow law for a material satisfying Huber-Mises' plasticity criterion with a yield stress of $\sigma_p = \sqrt{3}K$, that is Levy-Mises' rigid-plastic law:

$$\sigma = \frac{2}{3} \frac{\sigma_p}{\dot{\varepsilon}_i} \dot{\varepsilon} \quad (3)$$

The conditions of friction between the material and the tools are described by the Coulomb friction model and Treska's friction model, in which respective values of the friction coefficients and the friction factor are taken:

$$\begin{aligned} \tau_j &= \mu \cdot \sigma_n \text{ for } \mu \cdot \sigma_n < \frac{\sigma_0}{\sqrt{3}}, \\ \tau_j &= m \frac{\sigma_0}{\sqrt{3}} \text{ for } \mu \cdot \sigma_n > m \frac{\sigma_0}{\sqrt{3}}, \end{aligned} \quad (4)$$

where: τ_j – unit friction force vector, σ_0 – base stress, σ_n – normal stress, μ – friction coefficient, m – friction factor.

The boundary conditions of the heat transfer model are assumed as the combined limiting conditions of the second and third kinds, and are described by the formula:

$$k_x \frac{\partial T_s}{\partial x} l_x + k_y \frac{\partial T_s}{\partial y} l_y + k_z \frac{\partial T_s}{\partial z} l_z + q + \alpha(T_s - T_o) = 0 \quad (5)$$

where: l_x, l_y, l_z – directional cosines of the normal to the strip surface, q – heat flow rate on the cooled strip zone, α – heat transfer coefficient, T_o – ambient temperature.

The Forge2009® software enables the determination of the fields of temperature, stresses, strains and strain rates in the analyzed zone of metal being deformed. A substantial advantage that influences the accuracy of obtained computation results is the possibility of inputting the rheological properties of the deformed metal, either in the form of a mathematical function or in a tabularized form, reflecting the actual stress – strain relationships.

3. Results of numerical studies

The application of the Forge2009® software using the thermomechanical models incorporated in it requires the definition of boundary conditions which are crucial to the correctness of numerical computation. Therefore, computation results are particularly affected by: the properties of material examined, friction conditions, and the kinetic and thermal parameters describing the plastic working process. The stock and working tool models were made using a CAD type program, and then a finite element grid was plotted on them. When generating the finite element grid, grid elements were locally concentrated in the largest deformation zone, which assured good geometrical consistence of the stock after deformation to be obtained. Because of the symmetry of the process, the theoretical analysis was performed for 1/2 of the stock, which allowed a considerable reduction of the computation time.

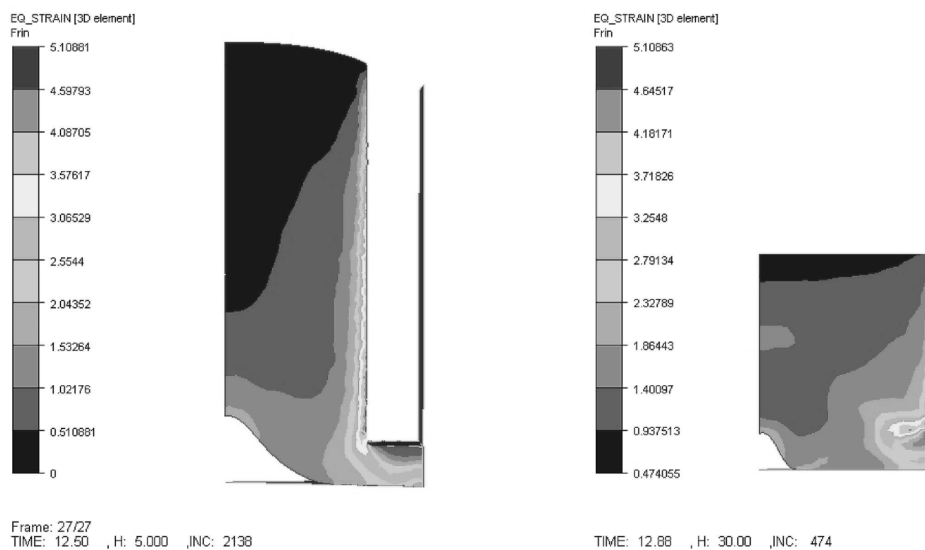



Fig. 2. Strain distribution – a 90° die: a) extrusion operation, b) compression operation

Aluminium Al99 acc. to the DIN standard was used as stock material for the studies; the properties of the material to be deformed were taken from the material database of the Forge2009® program. The initial stock height was equal to 100 mm, while the diameter of the deformed disk equalled 100 mm. The following initial conditions were assumed for both stages of numerical studies: friction coefficient $\mu = 0.1$, and friction factor $m = 0.2$; coefficient of heat exchange between the deformed metal and the tool, $\alpha - 1000 [W/Km^2]$; coefficient of heat exchange between the deformed metal and the air, $\alpha_p - 10 [W/Km^2]$; initial stock temperature, tool temperature and ambient temperature = 20°C.

Analysis was focused on the effect of the ram and die shapes allowing material without lapping to be obtained.

Figure 2 shows the distribution of strains in the extrusion operation and then in the multiaxial compression operation.

The strain values shown in Fig. 2 enable one to predict the flow of material during the extrusion operation. At the same time, it can be observed that the largest strain magnitudes exist at the ram surface. An occurring crater is also visible. In operation 2 of multiaxial compression, a lap forms, which moves into the material. Figure 3 presents the strain distribution in the material subjected to extrusion again. As a stock, material was used, which had been deformed in the extrusion and multiaxial compression operations with the aim of strain accumulation.

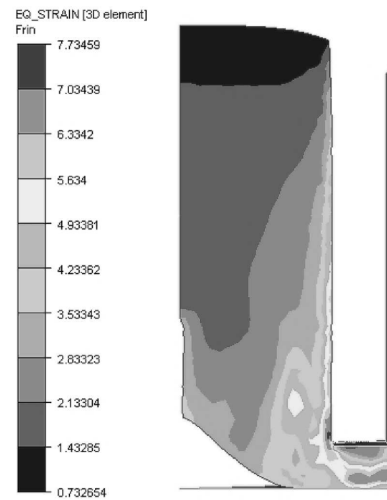

TIME: 12.50 ,H: 5.000 ,INC: 2327

Fig. 3. Strain distribution – the 90° die: extrusion operation, stage 3

The strain distributions shown in Fig. confirm that the lap formed at the multiaxial compression stage propagates into the material.

Figures 4 and 5 show stress distributions in the process of alternate extrusion and multiaxial compression.


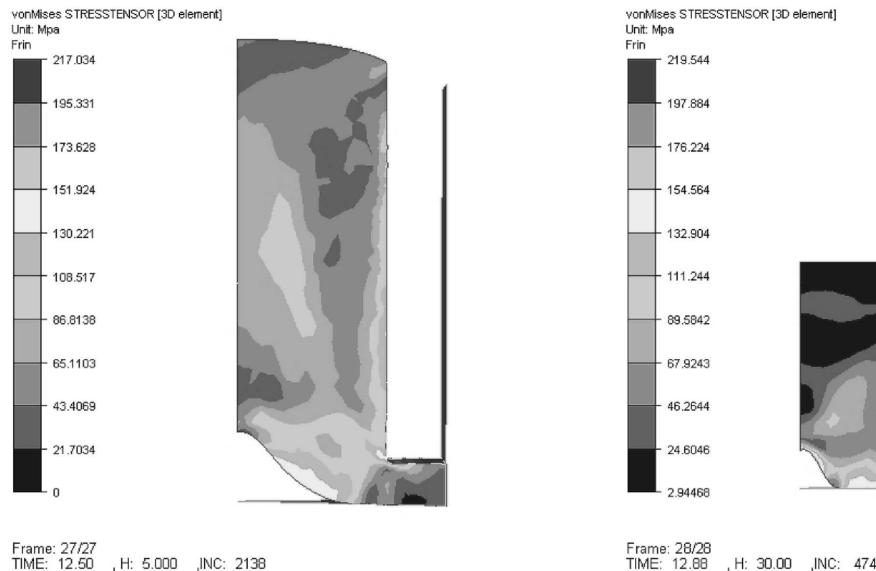


Fig. 4. Stress distribution – the 90° die: a) extrusion operation, b) compression operation


Fig. 5. Stress distribution – the 90° die: extrusion operation, stage 3

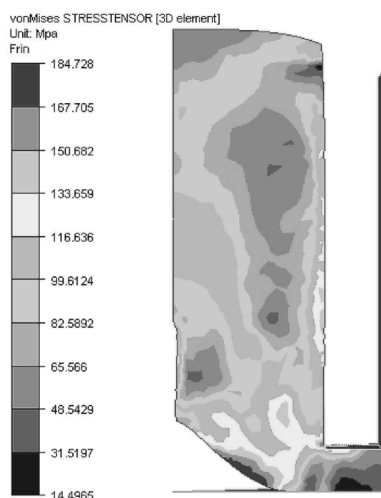

TIME: 12.50 , H: 5.000 ,INC: 2327

The stress distributions shown in Figs. 4 and 5 confirm the possibility of laps occurring in the material being deformed. It is therefore necessary to develop the appropriate die and ram shapes in order to prevent potential laps from occurring. Subsequent numerical simulations were conducted aimed at changing the die inclination angle to 95° and 100°.

The strain distributions for the modified die inclination angle, as shown in Fig. confirm that it is possible to reduce or completely eliminate the crater forming in the material axis. Further studies were conducted with the aim of reducing the potential for forming material lapping. To this end, the ram shape was modified. The results for strain distribution in the extrusion operation with different ram shapes are shown in Figure 7.

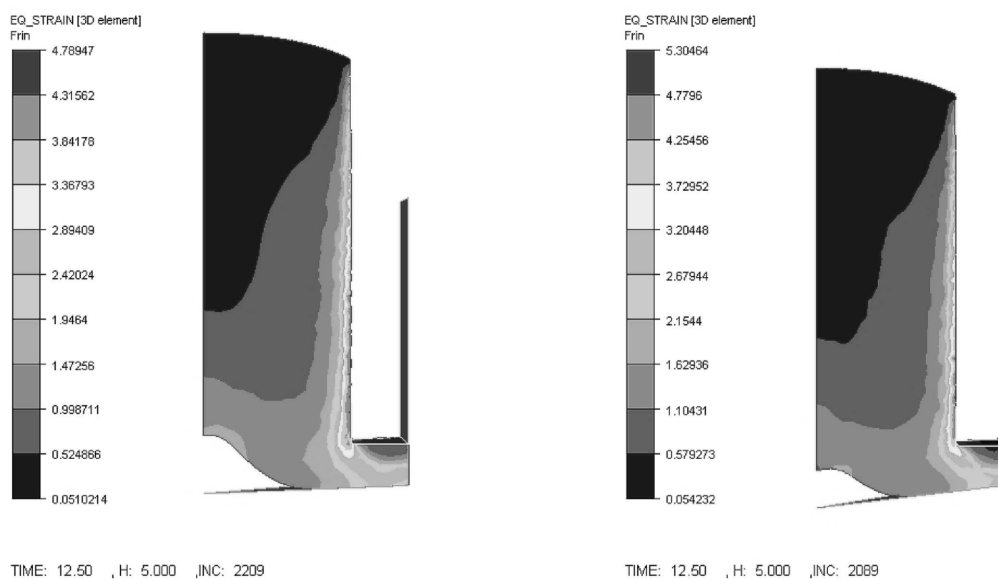

TIME: 12.50 , H: 5.000 ,INC: 2209

TIME: 12.50 , H: 5.000 ,INC: 2089

Fig. 6. Strain distribution, the extrusion operation: a) 95° die; b) 100° die

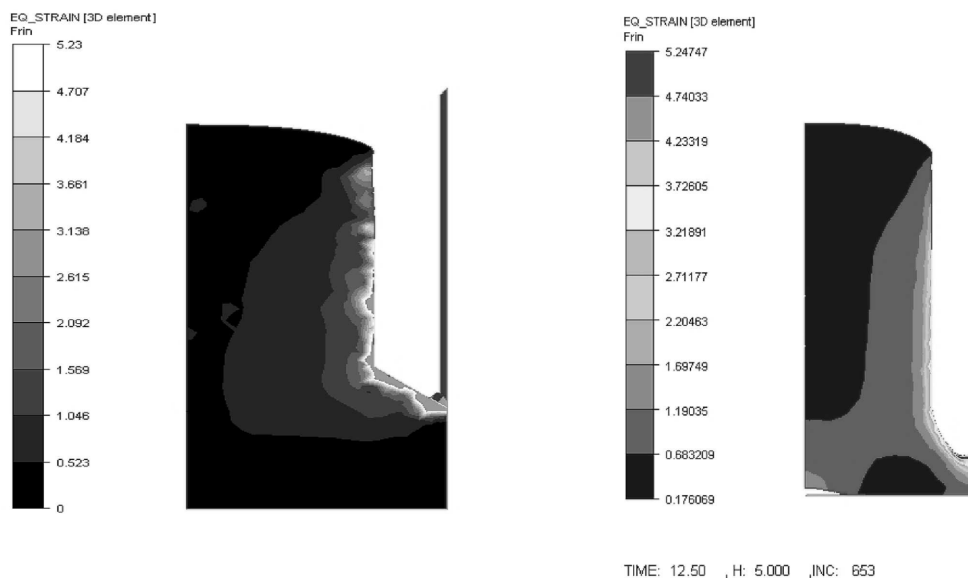


Fig. 7. Strain distribution, the extrusion operation: a) 45°-angle ram; b) rounded ram

The strain distribution results for the modified ram shape, as shown in Fig. 7, confirm the possibility of obtaining a greater strain homogeneity compared to the straight ram shown in Fig. 2a.

4. Summary

The paper presents the results of numerical simulations of the alternate indirect extrusion and multi-axial compression process, carried out using Forge 2009, commercial software designed for the thermomechanical analysis of plastic working processes. The novel method of alternate indirect extrusion and multi-axial compression, proposed by the authors, is characterized by the occurrence of strain states in the material being plastically worked, which are similar to those occurring in the processes of equal channel angular pressing and cyclic extrusion compression processes.

From the preliminary studies carried out it is found that the combination of the two alternate operations, i.e. extrusion and multi-axial compression, result in strain accumulation and the formation of a strain state particularly favourable to grain refinement.

The paper has also presented selected results concerning the distribution of strains and stresses in the process of alternate extrusion and multi-axial compression. Examples of die and ram shape modifications are also given and their influence on the strain distribution, as well as on the likelihood of occurrence of material lapping, are discussed. The presented results of the studies confirm the assertion that by the appropriate modification of the die and ram shapes it is possible to obtain

material of homogeneous properties within its entire volume.

The publication has been drawn up based on the study performed within the Research Project N N508 480838 entitled “Developing the methodology for the production of materials of ultrafine-grained and nanometric structure by alternate extrusion and multi-axial compression”, co-financed by the Ministry of Science and Higher Education of the Republic of Poland for the years 2010÷2012, carried out by the Czestochowa University of Technology.

REFERENCES

- [1] L. De Pari, A. Bandar, W. Van Geertruyden, W. Misiołek, Modeling of Hot Rolling 6061 Aluminum Alloy-State Variables And Grain Size Predictions, *Computer Methods in Materials Science* 7, 1, 11-16 (2007).
- [2] M. Kwapisz, H. Dyja, The Model of Grain Size Variation in The Aluminum Accumulative Roll-Bonding Process; *Proceedings of the International Conference on „Sovremenne dostizhenya v teorii y tekhnology plasticheskoy obrabotky metallov”* Petersburg, 16-20 (2007).
- [3] M. Kwapisz, M. Knapiński, H. Dyja, Matematyczny model zmian własności wytrzymałościowych aluminium poddawane go dużym odkształceniom plastycznym (A mathematical model for the variations in the mechanical properties of aluminium subjected to severe plastic deformations); *FIMM Conference*, 45-50 (2009).
- [4] M. Kwapisz, M. Knapiński, A. Kawałek, Analysis of variations of the mechanical properties of

- aluminium during the accumulative roll-bonding (ARB) process; *Hutnik – Wiadomości Hutnicze* 5, 340-343 (2009).
- [5] M. Kwapisz, Badanie procesu walcowania pakietowego aluminium i opracowanie modelu rozwoju mikrostruktury i własności mechanicznych (The study of the aluminium roll-bonding process and working out of the model for the development of the microstructure and mechanical properties). A doctoral dissertation, Częstochowa 2007.
- [6] P. B. Prangnell, J. R. Bowen, P. J. Apps, Ultra-fine grain structures in aluminum alloys by severe deformation processing, *Materials Science and Engineering* **A375-377**, 178-185 (2004).
- [7] K. Przybyłowicz, *Metaloznawstwo*, Wydawnictwo Naukowo-Techniczne, Warsaw 1992.
- [8] A. Rosochowski, L. Olejnik, M. Richert, Metal forming technology for producing bulk nanostructured metals, *Journal of Steel and Related Materials*, 2004, suppl. *Metal Forming*, 35-44 (2004).
- [9] N. Tsuji, Y. Saito, H. Utsunomiya, S. Tanigawa, Ultra-fine grained bulk steel produced by accumulative roll-bonding (ARB) process, *Scripta Materialia* **40**, 7, 795-800 (1999).